

Hypothetical Thermodynamic Properties: The Boiling and Critical Temperatures of Polyethylene and Polytetrafluoroethylene

James S. Chickos*

Department of Chemistry and Biochemistry, University of Missouri—St. Louis, St. Louis, Missouri 63121

The normal ($p = 101.325$ kPa) boiling-temperature behavior of a homologous series, T_B , as a function of the number of repeat units, N , is fit by a hyperbolic function whose limiting value asymptotically approaches $T_B(\infty) = (1217 \pm 246)$ K for series related to polyethylene and approximately $T_B(\infty) = 915$ K for those related to polytetrafluoroethylene. Normal boiling temperatures have been fit to the function $T_B = T_B(\infty)[1 - 1/(a_B N + b_B)]$ where a_B and b_B are constants characteristic of the series investigated. Similar behavior is observed for the critical temperature, T_C . As the number of repeat units, N , approaches infinity, T_B and T_C are found to converge. This provides an indirect method of determining $T_C(\infty)$. Combined with a few other experimentally determined critical temperatures, the T_C of an entire series can be predicted. Consistent with the convergence of T_B and T_C , the limiting critical pressure, $P_C(\infty)$, is found to approach 1 atm as N approaches infinity. The vaporization enthalpy and entropy at the boiling temperature, $\Delta_1^\beta H_m(T_B)$ and $\Delta_1^\beta S_m(T_B)$, used initially to suggest hyperbolic behavior of T_B , show complex behavior with increasing N . This behavior is discussed in terms of a simple mathematical model proposed previously.

Introduction

Hypothetical thermodynamic properties have been shown to provide information useful in the evaluation of thermochemical properties. For example, subcooled vaporization enthalpies evaluated at $T = 298.15$ K have been used to validate sublimation enthalpies of solids;¹ the distribution of polyaromatic hydrocarbons between the gas and particulate phase has been found to be proportional to the hypothetical subcooled liquid vapor pressure.² Melting temperatures of compounds that decompose before reaching the liquid state can be evaluated from solubility measurements and used to obtain estimates of fusion enthalpies; these values can be used subsequently in various other thermodynamic cycles.³

Most textbooks describing the physical properties of organic compounds point out that a homologous series shows regular increases in both normal melting and boiling temperatures as the size of the molecule increases. It has been shown, previously, that the melting temperature of the n -alkanes does not increase indefinitely but asymptotically approaches a limiting value, $T = 411$ K, as characterized by the melting temperature of polyethylene.^{4,5} In this article, the question of whether the normal boiling temperature of a homologous series, T_B , increases indefinitely or whether it too asymptotically approaches a limiting value is discussed.

The increase in the normal boiling temperature of a homologous series decreases with increasing size, requiring the use of nonlinear expressions to fit experimental data. Both third-order polynomials and exponential functions have been previously used to model this property.^{6,7} The polynomial expressions increase with increasing repeat unit, and therefore the boiling temperature is unbound. The exponential expression, eq 1, predicts that, as the number of carbon atoms M approaches infinity, the boiling

temperature approaches a finite limiting value, $T_B(\infty)$. The numerical values of the constants, c and d , determined experimentally, result in a value $T_B(\infty) = 1078$ K. The vaporization enthalpies at the normal boiling temperature ($\Delta_1^\beta H_m(T_B)$), the critical temperature (T_C), and critical pressure (P_C) were also found to approach finite limits as the size of the molecule increases.⁷ Equation 1 was empirically derived by Kreglewski and Zwolinski⁷ using results of Kurata and Isida⁸ on hole theory treatment of n -paraffin liquids. Kurata and Isida found that the effective length of a carbon skeleton should be proportional to the two-thirds power of the number of carbon atoms when $M > 5$.

$$T_B(M) = T_B(\infty) - ce^{-d}M^{2/3} \quad (1)$$

This paper reports a mathematical relationship empirically derived from Gibbs' equation that suggests that boiling temperatures of homologous series related to polyethylene and polyperfluoroethylene may asymptotically approach finite limits. Application of a model and the corresponding protocol recently used to predict the melting temperatures of homologous series is also applied to their boiling temperature and critical temperature and pressure.⁴ The limiting temperatures obtained are remarkably similar to those previously derived. The results support the previous model that suggested that boiling temperature, vaporization enthalpy at the boiling temperature, and the critical temperature and pressure of polymers are finite.

Sources of Data

The boiling-temperature data used in this study were obtained from a variety of sources. The major sources of data for each series reported are cited in the supplementary tables. Boiling temperatures for a few individual compounds have been obtained from some of the commercial chemical catalogs and handbooks. Vaporization enthalpies used in this study at the boiling temperature, $T = T_B$, are those from the API 44-TRC Handbook.⁹ Boiling tempera-

* To whom correspondence may be addressed. E-mail: jsc@umsl.edu.

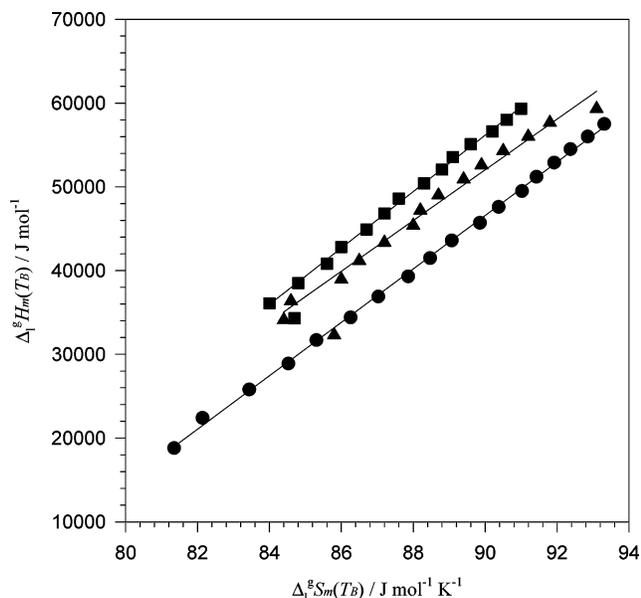


Figure 1. A plot of the $\Delta_1^g H_m(T_B)$ measured at $T = T_B$ vs the $\Delta_1^g S_m(T_B)$ also calculated at $T = T_B$ of ●, the *n*-alkanes (C_3 to C_{20}); ▲, *n*-alkylcyclopentanes (C_7 to C_{21}); ■, and *n*-alkylcyclohexanes (C_8 to C_{24}). The lines drawn through the data were obtained by a linear regression analysis. All the data were used for the *n*-alkanes; the triangle and square clearly off each respective line represents the value for ethylcyclopentane (C_7) and ethylcyclohexane (C_8), and each was not included in the regression analysis. The equations for each line are reproduced in Table 1.

tures for the *n*-alkanes are available from C_1 to C_{100} . Many of these are values that have been extrapolated from a variety of different mathematical relationships and are estimated. Experimental values for boiling temperature and vaporization enthalpy up to *n*- C_{20} have been used.^{9,10} Recommended critical properties were used when available.¹¹ Values from other sources were used to verify some of the data. Data for many of the same compounds can be found in the various compendia cited in the Supporting Information. Boiling temperature values differ depending on the source; qualitatively, the same conclusions were reached regardless of the source.

100 Is the Boiling Temperature of a Polymer Finite?

The model proposed to evaluate the limiting boiling temperatures of any homologous series related to polyethylene is similar to the one used in the evaluation of melting temperatures. In the limit, regardless of whether the parent compound is an alcohol, carboxylic acid, ester, halide, etc., if the boiling temperature of polyethylene is finite, the limiting boiling temperature of a homologous series of alcohols, carboxylic acids, esters, etc. should asymptotically approach the same finite limit, the boiling temperature of polyethylene. Evidence that suggests that the boiling temperature of a polymer may be finite is provided in Figure 1. In this figure, the vaporization enthalpies of the *n*-alkanes from C_3 to C_{20} (●), *n*-alkylcyclopentanes from C_7 to C_{21} (▲), and *n*-alkylcyclohexanes from C_8 to C_{24} (■) at their normal boiling temperatures are plotted against their corresponding entropy of vaporization, $\Delta_1^g S_m(T_B)$. With the exception of the first few members of each series, the plots are remarkably linear as indicated by their respective correlation coefficients, r^2 , reproduced in Table 1. The vaporization enthalpy of each of these compounds and a few other examples are expressed in linear form as a function of the entropy of vaporization by the equations

listed in Table 1. Since Gibbs' energy of vaporization at equilibrium conditions (T_B , $p = 101.325$ kPa) is zero, $\Delta_1^g S_m(T_B)$ may be replaced by $\Delta_1^g H_m(T_B)/T_B$ in the equations presented in Table 1. Solving for T_B results in eq 2 where m and C represent the slopes and intercepts of the lines in Figure 1. The slopes (m) and intercepts (C) are listed in Table 1. Equation 2 is the equation of a hyperbola that asymptotically approaches m as $\Delta_1^g H_m(T_B)$ approaches infinity. The slopes obtained from the equations in Figure 1 are different but similar in magnitude as are the intercepts; the intercepts are also large. If the vaporization enthalpy of an increasing chain is boundless, then the average of the slopes reported in Table 1 suggest a limiting boiling temperature, $T_B(\infty) \approx 3000$ K. This is discussed in more detail below.

$$T_B = m \Delta_1^g H_m(T_B) / (\Delta_1^g H_m(T_B) - C) \quad (2)$$

If the normal boiling temperature, T_B , of a homologous series is truly modeled by a hyperbolic function, as suggested by eq 2, and similar to what has been observed with melting temperature,⁴ then a plot of the function $1/[1 - T_B(N)/T_B(\infty)]$ against the number of repeat units of the homologous series, N , where $T_B(N)$ represents the normal boiling temperature of each member of the series, should result in a straight line.⁴ For series that converge to "polyethylene", N represents the number of methylene groups. Initial calculations using $T_B(\infty) = 3000$ K resulted in nonlinear plots; however, allowing $T_B(\infty)$ to vary resulted in the representative plots shown in Figure 2. The linear relationship observed between N and $1/[1 - T_B(N)/T_B(\infty)]$ for the compounds plotted in Figure 2 (and for all the compounds of Table 2) provided analytical expressions that could be solved for T_B in terms of $T_B(\infty)$, N , and two parameters, a_B and b_B , the slope and intercept of the plots in Figure 2, respectively. Solving for T_B in terms of $T_B(\infty)$, N , a_B , and b_B results in eq 3

$$T_B = T_B(\infty)(1 - 1/(a_B N + b_B)) \quad (3)$$

Experimental boiling-temperature data were then fit to this expression by a nonlinear least-squares program. Input parameters included T_B and N , the normal boiling temperature and the number of repeat units, respectively. The best values of a_B and b_B were calculated for each value of $T_B(\infty)$. The value of $T_B(\infty)$ was allowed to vary until a minimum in the sum of the squared differences between calculated and experimental was realized. This procedure was repeated for each series of compounds for which sufficient T_B data could be found. For most of the calculations described below, $T_B(\infty)$ was minimized in increments of 5 K. The results are summarized in Table 2.

According to the model proposed, if in the limit the homologous series chosen ultimately converges to the same "polymer", then the same limiting boiling temperature, $T_B(\infty)$, would be expected. Experimental boiling temperatures are available up to approximately 650 K. Since in many instances this requires relatively few repeat units to reach this limit ($N < 20$), the uncertainty in $T_B(\infty)$ evaluated in this manner would be expected to be significant. However, the results obtained for $T_B(\infty)$ for various homologous series related to polyethylene (column 2, Table 2) show remarkable constancy in this value. Some series such as the 1-alkanols and the *n*-alkyl cyanides do show larger values for $T_B(\infty)$. However, the *n*-alkanoic acids and the 2-alkanols are fit by more normal values of $T_B(\infty)$, suggesting that the values calculated for the 1-alkanols and *n*-alkyl cyanides are not anomalies but rather more indica-

Table 1. Correlation Equations of Figures 1 and 2 Obtained by Plotting $\Delta_1^g H_m(T_B)$ vs $\Delta_1^g S_m(T_B)$

<i>n</i> -alkanes	$\Delta_1^g H_m(T_B) = (3190.7 \pm 22.6) \Delta_1^g S_m(T_B) - (240583 \pm 350)$	$r^2 = 0.9992$
<i>n</i> -1-alkenes	$\Delta_1^g H_m(T_B) = (2469.3 \pm 109.7) \Delta_1^g S_m(T_B) - (169585 \pm 951)$	$r^2 = 0.9806$
<i>n</i> -alkylbenzenes	$\Delta_1^g H_m(T_B) = (3370.5 \pm 37.3) \Delta_1^g S_m(T_B) - (169585 \pm 951)$	$r^2 = 0.9806$
<i>n</i> -alkylcyclopentanes	$\Delta_1^g H_m(T_B) = (3028.8 \pm 97.4) \Delta_1^g S_m(T_B) - (220567 \pm 926)$	$r^2 = 0.9877$
<i>n</i> -alkylcyclohexanes	$\Delta_1^g H_m(T_B) = (3717.8 \pm 87.3) \Delta_1^g S_m(T_B) - (284890 \pm 999)$	$r^2 = 0.9918$
<i>n</i> -alkanethiols	$\Delta_1^g H_m(T_B) = (2268.7 \pm 162.6) \Delta_1^g S_m(T_B) - (161693 \pm 1728)$	$r^2 = 0.9558$

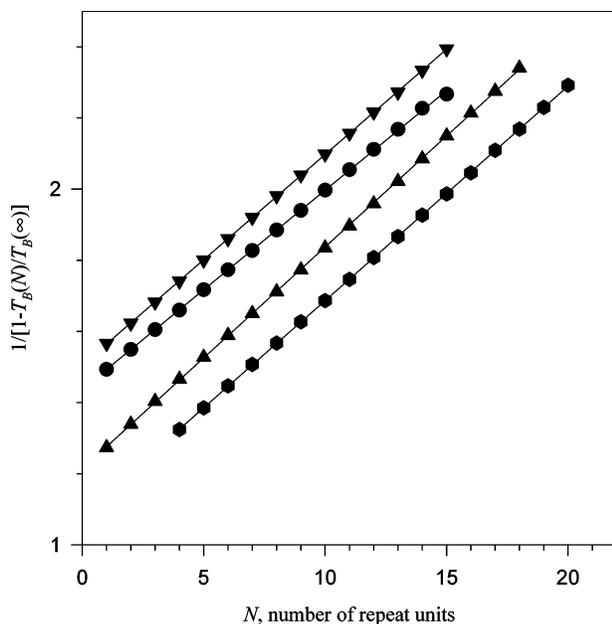


Figure 2. A plot of $1/[1 - T_B(N)/T_B(\infty)]$ against the number of repeat units, N ; ●, *n*-1-alkenes; ▲, *n*-alkanes; ■, *n*-alkylcyclopentanes; ◆, *n*-alkylcyclohexanes.

185 tive of the uncertainty in $T_B(\infty)$ evaluated in this manner.
 186 Averaging all the limiting temperatures results in a value
 187 of $T_B(\infty) = (1217 \pm 246)$ K. This value compares quite
 188 favorably to the value of $T_B(\infty) = 1078$ K reported by
 189 Kreglewski and Zwolinski (1021 K by Somayajulu)¹⁰ for the
 190 *n*-alkanes using eq 1.⁷ Table 2 summarizes the values of
 191 a_B and b_B obtained by the nonlinear least-squares program
 192 associated with each value of $T_B(\infty)$ obtained by best fit and
 193 the standard deviation between experimental and calculated
 194 values that results (columns 3–5). Also included in the
 195 table are the results obtained by using the average
 196 value $T_B(\infty) = (1217 \pm 246)$ K (columns 6–8). This results
 197 in the averaged values a_{Bm} and b_{Bm} . The number of data
 198 points associated with each correlation is indicated in the
 199 last column. A comparison of the standard deviation
 200 between experimental and calculated boiling temperature
 201 for both series of correlations (columns 5 and 8) suggests
 202 that for most compounds the calculated boiling tempera-
 203 ture is within the experimental uncertainty of the mea-
 204 surement and that using the mean value for $T_B(\infty)$ does
 205 not significantly affect the quality of the fit.

206 A value of $T_B(\infty) = (1217 \pm 246)$ K is considerably less
 207 than $T_B(\infty) = 3000$ K, the value suggested from the slopes
 208 of the lines in Table 1 according to eq 2. A limiting value
 209 of $T_B(\infty) = 3000$ K would be approached only if $\Delta_1^g H_m(T_B)$
 210 is boundless. However, if $\Delta_1^g H_m(T_B)$ also remains finite as
 211 $N \rightarrow \infty$, this limiting value may not be approached.
 212 Rearranging eq 2 and solving for $\Delta_1^g H_m(T_B)$ results in eq 4

$$\Delta_1^g H_m(T_B)_{\max} = CT_B/(mT_B) \quad (4)$$

213 The limiting value of the vaporization enthalpy,
 214 $\Delta_1^g H_m(T_B)_{\max}$, can be obtained by substituting $T_B(\infty) = (1217$

215 $\pm 246)$ K and the values of m and C from the equations in
 216 Table 1. Doing so results in a mean value of $\Delta_1^g H_m(T_B)_{\max}$
 217 $= (147 \pm 30)$ kJ·mol⁻¹. Since, in the limit, the structure
 218 of the compounds in Table 1 are most closely related
 219 to polyethylene, this value must approximate the maxi-
 220 mum vaporization enthalpy experienced by an increasing
 221 chain of methylene groups, provided the maximum occurs
 222 at fairly large values of N . Furthermore, the fact that
 223 $\Delta_1^g H_m(T_B)_{\max}$ is finite suggests that the ascending portion
 224 of the vaporization enthalpy may also be modeled by a
 225 hyperbolic function of the number of repeat units. If this
 226 is the case, a plot of $[1/(1 - \Delta_1^g H_m(T_B)/\Delta_1^g H_m(T_B)_{\max})]$ vs
 227 N should result in a linear correlation; alternatively, the
 228 vaporization enthalpy of each member of a homologous
 229 series should be related to $\Delta_1^g H_m(T_B)_{\max}$ by eq 5

$$\Delta_1^g H_m(T_B) = \Delta_1^g H_m(T_B)_{\max} (1 - 1/(a_H N + b_H)) \quad (5)$$

230 Figures 3 and 4 illustrate the behavior observed. Typical
 231 plots of $[1/(1 - \Delta_1^g H_m(T_B)/\Delta_1^g H_m(T_B)_{\max})]$ vs N for the
 232 *n*-1-alkenes (●) and *n*-alkylcyclohexanes (■) are shown in
 233 Figure 3 and Figure 4 shows the experimental (symbols)
 234 and calculated vaporization enthalpies (lines) for the
 235 *n*-alkanes (●), *n*-alkanethiols (▲), and *n*-alkylcyclopent-
 236 anes (■). Values of the adjustable parameters of eq 5
 237 and the standard deviation of each fit associated with a
 238 $\Delta_1^g H_m(T_B)_{\max} = 147$ kJ·mol⁻¹ is provided in Table 3.
 239 Additional discussion of the behavior of vaporization en-
 240 thalpy with increasing N is provided below.

Is the Critical Temperature of a Polymer Finite?

242 Ambrose's equation for the critical temperature of the
 243 *n*-alkanes, T_C , is given by eq 6.¹² The terms c and d refer
 244 to constants, and N represents the number of methylene
 245 groups. Though not intended to be applied to high molecu-
 246 lar weight alkanes,¹⁰ this equation relates the critical
 247 temperature to boiling temperature. This equation pre-
 248 dicted that $T_C \rightarrow T_B$ as $N \rightarrow \infty$. If T_B can be fit by a hyper-
 249 bolic function, then it seemed reasonable according to eq 6
 250 that this approach should also work for T_C . Substitution
 251 of T_C for T_B in eq 3 results in eq 7


$$T_C = T_B + T_B/[c + d(N + 2)] \quad (6)$$

$$T_C = T_C(\infty)(1 - 1/(a_C N + b_C)) \quad (7)$$

252 Using the critical temperatures of the *n*-alkanes from
 253 propane ($N = 1$) to docosane ($N = 20$),¹¹ a nonlinear least-
 254 squares treatment provided values of a_C and b_C as a
 255 function of $T_C(\infty)$. Allowing $T_C(\infty)$ to vary by the nonlinear
 256 least-squares procedure described above resulted in $T_C(\infty)$
 257 $= 1050$ K, a value in good agreement with limiting boiling
 258 temperature of $T_B(\infty) = (1217 \pm 246)$ K. Similar results
 259 were obtained for several other homologous series that
 260 included the *n*-alkanals, the alkanic acids, the 2- and
 261 3-alkanones, the 1-alkenes, 1-alkanols, etc. The best-fit
 262 values of a_C and b_C derived for all the series examined are
 263 listed in the first five columns of Table 4. The limiting
 264 values of $T_C(\infty)$ are all well within the uncertainty of the

D Journal of Chemical and Engineering Data
Table 2. Results Obtained by Treating T_B of a Series of Homologous Compounds as Function of the Number of Repeat Units, N , and Allowing $T_B(\infty)$ to Vary According to Equation 3; a_{Bm} , b_{Bm} : Values of a_B and b_B Obtained by Using the Mean Value of $T_B(\infty) = 1217$ K

polyethylene series	$T_B(\infty)/K$	a_B	b_B	$\pm\sigma/K$	a_{Bm}	b_{Bm}	$\pm\sigma/K$	data points
<i>n</i> -alkanes	1076	0.06231	1.214	0.9	0.04694	1.1984	3.6	18
2-methyl- <i>n</i> -alkanes	1110	0.05675	1.3164	0.2	0.0461	1.2868	0.3	8
<i>n</i> -alk-1-enes	1090	0.06025	1.265	0.4	0.04655	1.242	2.7	17
<i>n</i> -alkylcyclopentanes	1140	0.05601	1.4369	0.6	0.04732	1.4037	1.3	15
<i>n</i> -alkylcyclohexanes	1120	0.05921	1.5054	0.1	0.04723	1.4543	1.2	13
<i>n</i> -alkylbenzenes	1140	0.05534	1.5027	1.1	0.05684	1.5074	1.4	15
1-amino- <i>n</i> -alkanes	1185	0.04893	1.274	3.4	0.04607	1.267	3.4	15
1-chloro- <i>n</i> -alkanes	1125	0.05717	1.2831	0.3	0.04775	1.2628	1.6	13
1-bromo- <i>n</i> -alkanes	1125	0.05740	1.3264	1.0	0.0481	1.2993	1.5	12
1-fluoro- <i>n</i> -alkanes	1075	0.05833	1.2214	0.4	0.04495	1.1987	2.1	9
1-hydroxy- <i>n</i> -alkanes	1820	0.01806	1.220	0.8	0.03953	1.3559	3.6	12
2-hydroxy- <i>n</i> -alkanes	1055	0.05131	1.4923	1.8	0.03732	1.4031	1.8	7
<i>n</i> -alkanals	910	0.08139	1.4561	1.4	0.04277	1.3177	2.5	7
2-alkanones	1440	0.03071	1.2905	1.6	0.0430	1.3613	1.7	8
<i>n</i> -alkane-1-thiols	1090	0.06170	1.3322	0.2	0.042	1.3635	2.8	14
sym <i>n</i> -dialkyl disulfides	1190	0.08720	1.4739	0.4	0.08207	1.4608	0.6	9
<i>n</i> -alkylnitriles	1855	0.01907	1.2294	2.6	0.04295	1.3869	3.4	11
<i>n</i> -alkanoic acids	1185	0.0440	1.4964	1.3	0.04100	1.4790	1.3	16
methyl <i>n</i> -alkanoates	1395	0.03158	1.3069	2.6	0.04200	1.3635	2.8	10

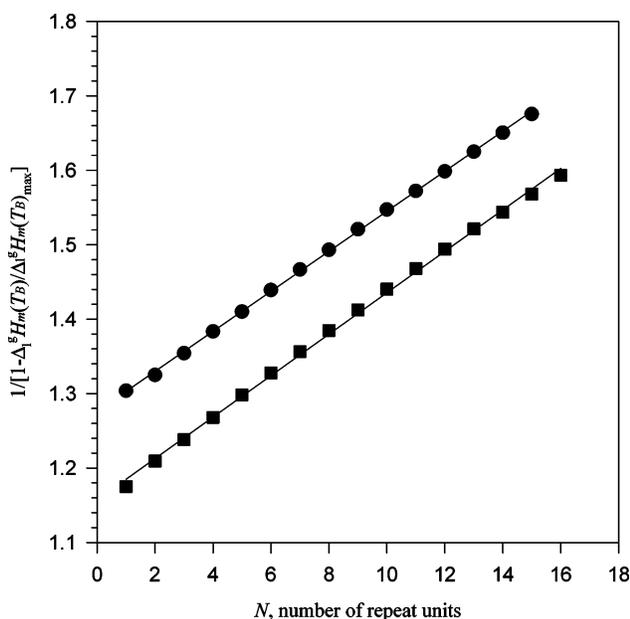
Figure 3. A plot of $1/[1 - \Delta_1^g H_m(T_B)/\Delta_1^g H_m(T_B)_{\max}]$ vs the number of repeat units for the: ●, 1-alkenes; and ■, *n*-alkylcyclohexanes using a value of $\Delta_1^g H_m(T_B)_{\max} = 147$ kJ·mol⁻¹.

265 method. A mean value of $T_C(\infty) = (1068 \pm 68)$ K was
 266 obtained. A comparison of the limiting $T_B(\infty)$ and $T_C(\infty)$
 267 values and their uncertainties suggest that the values are
 268 within experimental error of each other; both appear to
 269 converge at approximately 1150 K. Since the data available
 270 for T_C is likely to be more uncertain, the limiting value
 271 derived from boiling temperatures, $T_C(\infty) = T_B(\infty) = (1217$
 272 $\pm 246)$ K, has been used in all subsequent calculations.
 273 The use of this value resulted in fits to experimental T_C
 274 data by the lines drawn in Figure 5 for several of the series
 275 examined. Additional details are provided in the caption
 276 associated with Figure 5. Columns 5 and 9 of Table 4
 277 compare the standard deviation obtained by a nonlinear
 278 least-squares fit and the results calculated using $T_C(\infty) =$
 279 1217. In most cases the errors are comparable. A similar
 280 value, $T_C(\infty) = 1021$ K, has been reported by Somayajulu
 281 using a different mathematical approach.¹⁰

282 The convergence of T_C with T_B has several further
 283 implications. As T_C approaches T_B , $\Delta_1^g H_m(T_B)$ must ap-
 284 proach zero.¹⁰ The fact that the $\Delta_1^g H_m(T_B)$ first increases

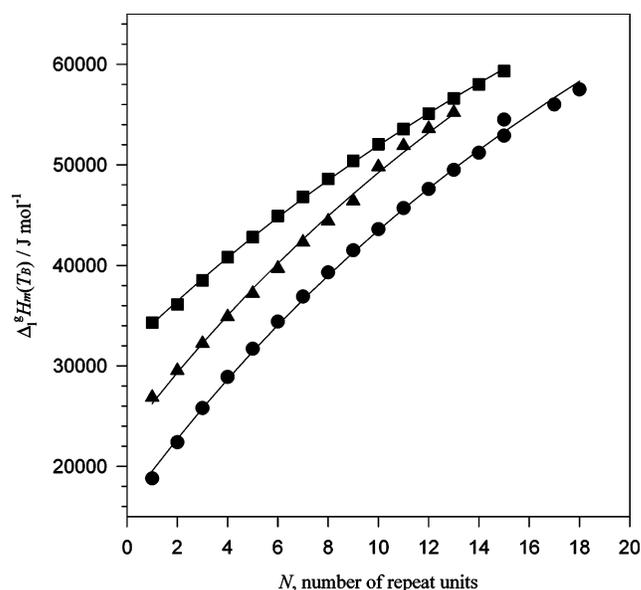

Figure 4. Vaporization enthalpies at the normal boiling temperature of the ●, *n*-alkanes; ▲, 1-alkanethiols; and ■, alkylcyclopentanes as a function of the number of repeat units. The lines were calculated with the aid of eq 5 using the value $\Delta_1^g H_m(T_B)_{\max} = 147$ kJ·mol⁻¹.


Table 3. Values of the Parameters of a_H and b_H Generated in Fitting $\Delta_1^g H_m(T_B)$ of Several Homologous Series Using Equation 5 and a Value of $\Delta_1^g H_m(T_B)_{\max} = 147$ kJ·mol⁻¹

	a_H	b_H	$\pm\sigma/kJ\cdot mol^{-1}$	data points
<i>n</i> -alkanes	0.02960	1.1235	0.4	18
<i>n</i> -alkylbenzenes	0.02741	1.284	0.5	15
<i>n</i> -alkylcyclohexanes	0.02697	1.2754	0.2	15
<i>n</i> -alkylcyclopentanes	0.02821	1.2475	0.2	15
<i>n</i> -alk-1-enes	0.02796	1.1554	0.4	17
<i>n</i> -alkane-1-thiols	0.03172	1.1854	0.5	13

285 as a function of N suggests that there must be some
 286 point at which it reaches a maximum before decreasing to
 287 zero as the temperature approaches 1217 K. Even the value
 288 of $\Delta_1^g H_m(T_B)_{\max}$ suggested by the slope of eq 5 may not be
 289 realized; $\Delta_1^g H_m(T_B)$ must begin to decrease at some point
 290 with increasing T_B . Equation 8 reported by Somayajulu¹⁰
 291 provides a means of describing the possible behavior of
 292 $\Delta_1^g H_m(T_B)$ as a function of T_B and T_C

Table 4. Results Obtained for the Constants a_c and b_c by Treating T_C as a Function of the Number of Repeat Units, N , According to Equation 7 and Allowing $T_C(\infty)$ to Vary; a_{cm} , b_{cm} : Values of a_c and b_c Obtained by Using the Mean Value of $T_C = 1217$ K


polyethylene series	$T_C(\infty)/K$	a_c	b_c	$\pm\sigma/K$	$T_C(\infty)/K$	a_{cm}	b_{cm}	$\pm\sigma/K$	data points
<i>n</i> -alkanes	1050	0.1292	1.4225	1.7	1217	0.07445	1.4029	9.8	16
<i>n</i> -alkanals	1070	0.11708	1.7753	1.0	1217	0.077557	1.6355	1.8	8
alkanoic acids	1105	0.0961	2.1137	3.4	1217	0.06456	1.9329	3.9	31
1-alkanols	1045	0.11567	1.8362	3.6	1217	0.06773	1.6639	4.7	11
2-alkanones	1105	0.10063	1.8371	1.3	1217	0.071932	1.718	1.9	11
3-alkanones	1185	0.07827	1.8168	1.3	1217	0.07158	1.7811	1.3	10
1-alkenes	1035	0.1327	1.5496	0.3	1217	0.08278	1.4518	3.1	8
2-methylalkanes	950	0.16282	1.7767	0.6	1217	0.078619	1.53289	1.7	5

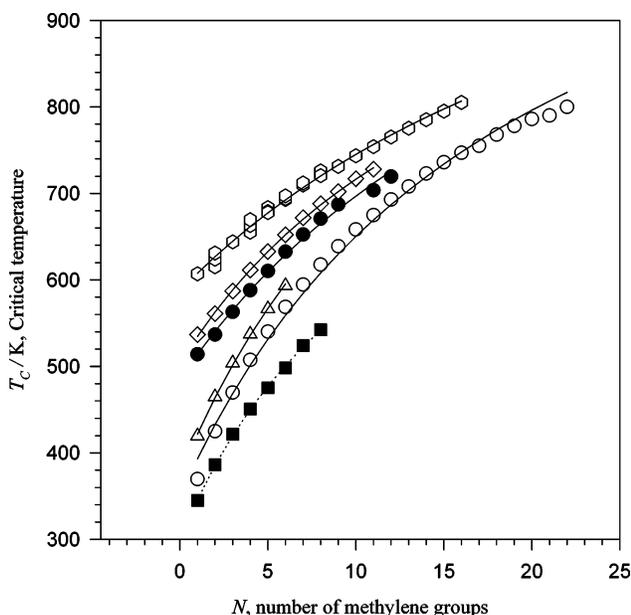
Figure 5. A plot of experimental critical temperatures vs N , the number of methylene groups for (top to bottom) the \circ , alkanolic acids; \diamond , 2-alkanones; \bullet , 1-hydroxalkanes; Δ , 1-alkenes; \circ , the *n*-alkanes; and \blacksquare , *n*-perfluoroalkanes. The lines were calculated using eq 7 and values of $T_C(\infty) = 1217$ K for the hydrocarbons and derivatives and $T_C(\infty) = 915$ K for the fluorocarbons (squares); values of a_c and b_c are listed in columns 7 and 8 of Tables 4 and 8, respectively.

$$\Delta_1^g H_m(T_B) = e_1 X + e_2 X^2 + e_3 X^3 + e_4 X^4 \quad \text{where} \\ X = (T_C - T_B)/T_C \quad (8)$$

293 To calculate the anticipated behavior of $\Delta_1^g H_m(T_B)$ as a
 294 function of N according to this model, values of T_B and T_C
 295 for the *n*-alkanes were calculated using eqs 3 and 7; values
 296 for a_c and b_c that correspond to the limiting temperature,
 297 $T_B(\infty) = T_C(\infty) = 1217$ K (columns 6–8, Table 4), were also
 298 used. Experimental $\Delta_1^g H_m(T_B)$ values for the *n*-alkanes
 299 were then fit to eq 8 using calculated values of T_B and T_C
 300 and allowing the constants e_1 – e_4 to vary through a least-
 301 squares process. The resulting values of e_1 – e_4 for both the
 302 *n*-alkanes and 1-alkenes are listed in Table 5.

303 The behavior of $\Delta_1^g H_m(T_B)$ calculated as a function of both
 304 the number of repeat units, N , and $\Delta_1^g S_m(T_B)$ according to
 305 eq 8, is illustrated in Figures 6 and 7. The circles represent
 306 experimental data for the *n*-alkanes, and the fitted lines

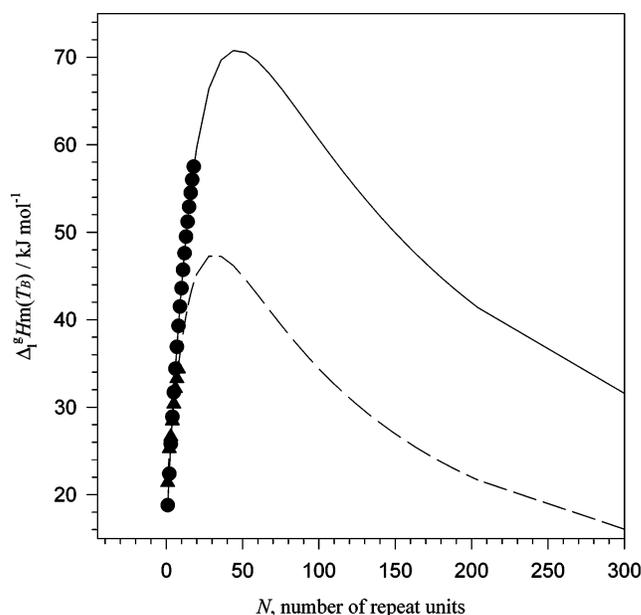
Figure 6. Values of $\Delta_1^g H_m(T_B)$ as a function of the number of repeat units. *n*-Alkanes: solid line, calculated values; \bullet , experimental values. *n*-Perfluoroalkanes: dashed line, calculated values; \blacktriangle , experimental values.

307 correspond to the behavior predicted by eq 8. According to
 308 Figure 6, a maximum of approximately $70 \text{ kJ}\cdot\text{mol}^{-1}$ is
 309 predicted at about $N = 50$ for $\Delta_1^g H_m(T_B)$. The results
 310 obtained for the 1-alkenes (not shown) were similar as were
 311 the results obtained by Somayajulu¹⁰ using eq 8; both
 312 calculations used the same experimental data but different
 313 equations for calculating T_B and T_C . The linear behavior
 314 between $\Delta_1^g H_m(T_B)$ and $\Delta_1^g S_m(T_B)$ observed in Figure 1 for
 315 the *n*-alkanes is also evident in Figure 7. The experimental
 316 points cover only a small portion of this curve. The largest
 317 linear portion is experimentally inaccessible and therefore
 318 speculative.¹³

Critical Pressures

319
 320 The convergence of T_C with T_B as $N \rightarrow \infty$ has a further
 321 implication. Since T_B represents the normal boiling temper-
 322 ature, P_C must approach one atmosphere as the two
 323 temperatures converge. Critical pressures are known to
 324 decrease with molecular size. A variety of different func-
 325 tions can be used to model the data, each resulting with a
 326 different quality of fit and somewhat different predictions.
 327 We have chosen to use a minimum number of adjustable

Table 5. Constants of Equation 8 Used in Fitting $\Delta_1^g H_m(T_B)$

	e_1	e_2	e_3	e_4	$\pm\sigma/\text{kJ}\cdot\text{mol}^{-1}$
<i>n</i> -alkanes	1418.385	−9269.807	21935.55	−18508.375	0.1
<i>n</i> -1-alkenes	1427.21	−9194.337	21978.0	−19492.425	0.1
<i>n</i> -perfluoroalkanes	1091.54	−8393.756	25093.20	−27838.635	0.3

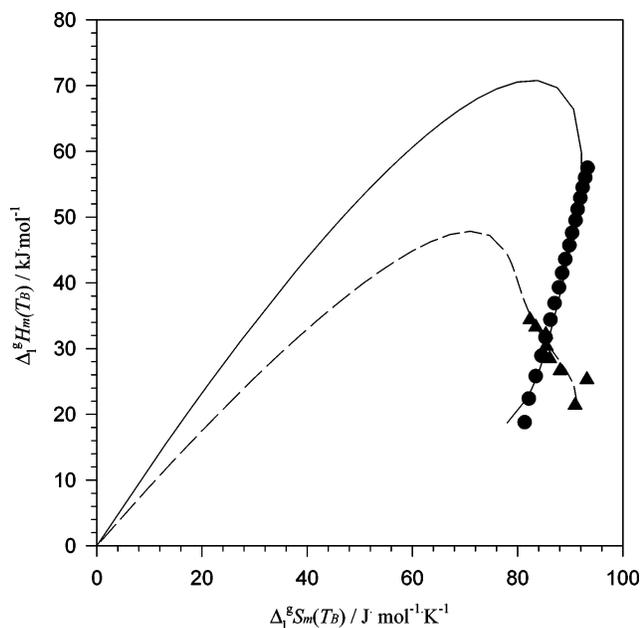


Figure 7. Experimental values of $\Delta_1^b H_m(T_B)$ as a function of $\Delta_1^b S_m(T_B)$. *n*-Alkanes: ●, experimental values; solid line, calculated values. *n*-Perfluoroalkanes: ▲, experimental values; dashed line, calculated values.

328 parameters to fit the data. An additional restriction was
 329 that the function converge to some limiting value with
 330 increasing N . Ambrose's equation provides an empirical
 331 basis for using a hyperbolic function to model both T_B and
 332 T_C . Of interest was whether a similar simple function could
 333 fit the experimental data and also approach a limiting
 334 pressure of $P_C(\infty) = 101.325$ kPa. A plot of $1/[1 - P_C(\infty)/$
 335 $P_C]$ vs N resulted in satisfactory linear plots for each of
 336 the series investigated when $P_C(\infty) = 101.325$ kPa. This
 337 suggested that the data could be fit with only two adjust-
 338 able parameters. Solving for P_C as a function of N resulted
 339 in eq 9. Similar hyperbolic functions were used to model
 340 T_C and $\Delta_1^b H_m(T_B)$. The experimental critical pressures^{11,12}

$$P_C = P_C(\infty) / [1 - 1/(a_{PC}N + b_{PC})] \quad (9)$$

341 plotted as a function of the number of repeat units are
 342 reproduced in Figure 8 for the 1-alkanols, the *n*-alkanes,
 343 and the 2-methylalkanes. The lines characterize the calcu-
 344 lated fit. Figure 9 illustrates the fits obtained for the
 345 alkanolic acids and the 1-alkenes. The a_{PC} and b_{PC} param-
 346 eters reported in Table 6 were evaluated by a nonlinear
 347 least-squares analysis. The number of entries, N , the stand-
 348 ard deviation associated between experimental and calcu-
 349 lated values for each series, and the correlation coefficients,
 350 r^2 , are also provided. Given the uncertainty in experimen-
 351 tal P_C values (see Figure 9), a limiting pressure of 0.101 MPa
 352 is certainly plausible according to this analysis.

Modeling T_B and $\Delta_1^b H_m(T_B)$ of Series Related to Polytetrafluoroethylene

355 The series examined thus far all converge experimentally
 356 in the limit to polyethylene. If the boiling temperatures of
 357 liquids with structures related to polyethylene converge to
 358 a finite value, then similar boiling temperature behavior
 359 would be expected for series converging to other polymers.
 360 Unfortunately experimental thermochemical data for many
 361 other series are not available. Sufficient data for the *n*-per-
 362 fluorinated alkanes, 14 entries from C_3 to C_{16} , and the
 363 *n*-perfluorinated carboxylic acids, 8 entries ranging from

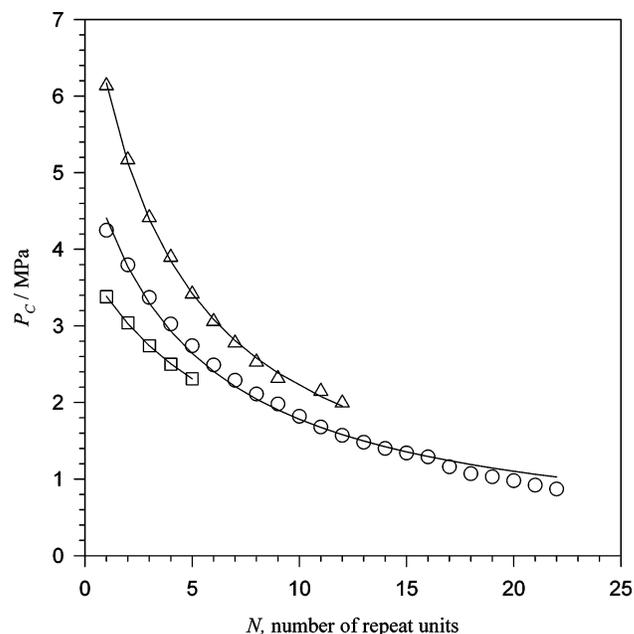


Figure 8. A plot of the critical pressure versus the number of repeat units for (top to bottom): Δ , the 1-alkanols; \circ , the *n*-alkanes; and \square , the 2-methylalkanes.

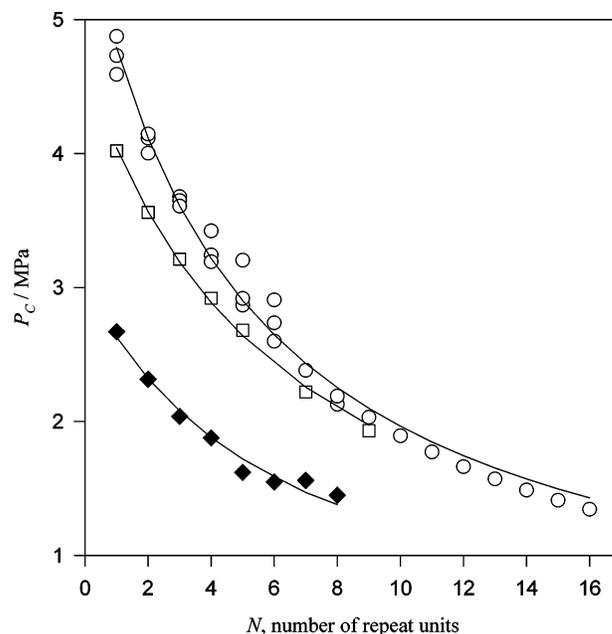


Figure 9. A plot of the critical pressure vs the number of repeat units for: \circ , *n*-alkanoic acids; \square , 1-alkenes; and \blacklozenge , perfluoroalkanes. The data for the alkanolic acids includes a few multiple determinations to give the reader a sense of the scatter in the experimental data.

Table 6. Values of the Parameters of a_{PC} and b_{PC} Generated in Fitting P_C of Several Homologous Series Using Equation 9 and $P_C(\infty) = 0.101325$ MPa

	a_{PC}	b_{PC}	$\pm \sigma/\text{MPa}$	N	r^2
<i>n</i> -alkanals	0.003181	1.017	0.08	8	0.9911
<i>n</i> -alkanes	0.004089	1.019	0.09	22	0.9970
alkanoic acids	0.003643	1.018	0.11	16	0.9937
1-alkanols	0.003454	1.013	0.05	11	0.9953
1-alkenes	0.003555	1.022	0.03	7	0.9975
2-methylalkanes	0.003763	1.027	0.20	5	0.9997

C_1 to C_{14} , were found in the literature. If these series
 364 behave similarly to those just examined, the boiling temper-
 365 atures of both these materials would be expected to
 366

Table 7. Values of the Parameters of a_B and b_B Generated in Fitting T_B of Several Homologous Perfluorinated Series Using Equation 3 and Allowing $T_{B(\infty)}$ to Vary in 5 K Increments; a_{Bm} , b_{Bm} : Values of a_B and b_B Using an Average Value of $T_{B(\infty)} = 915$ K

	$T_{B(\infty)}/K$	a_B	b_B	$\pm\sigma/K$	$T_{B(\infty)}/K$	a_{Bm}	b_{Bm}	$\pm\sigma/K$	N
<i>n</i> -perfluoroalkanes	880	0.07679	1.2905	2.1	915	0.06965	1.2816	2.2	13
<i>n</i> -perfluoroalkanoic acids	950	0.06313	1.5765	1.2	915	0.07053	1.6085	1.3	8
methyl <i>n</i> -perfluoroalkanoates					915	0.06637	1.5000	1.6	4
1-iodo- <i>n</i> -perfluoroalkanes					915	0.07409	1.3751	1.8	5

Table 8. Results Obtained for the Constants a_C and b_C by Treating T_C as Function of the Number of Repeat Units, N , According to Equation 7; a_{Cm} , b_{Cm} : Values of a_C and b_C Obtained by Using the Mean Value of $T_{C(\infty)} = 915$ K

polyperfluoroethylene series	$T_{C(\infty)}/K$	a_C	b_C	$\pm\sigma/K$	$T_{C(\infty)}/K$	a_{Cm}	b_{Cm}	$\pm\sigma/K$	N
<i>n</i> -perfluoroalkanes	920	0.1166	1.4813	1.1	915	0.1203	1.487	1.6	8

Table 9. Results Obtained for the Constants a_{PC} and b_{PC} by Treating P_C as Function of the Number of Repeat Units, N , and Using $P_{C(\infty)} = 0.101$ MPa According to Equation 9

polyperfluoroethylene series	$P_{C(\infty)}/MPa$	a_C	b_C	$\pm\sigma/MPa$	r^2	data points
<i>n</i> -perfluoroalkanes	0.1013	0.003555	1.0344	0.06	0.9703	8

converge to boiling temperature of polyperfluoroethylene.

Treating the experimental boiling points of the *n*-perfluorinated alkanes and carboxylic acids according to eq 3, and minimizing the error by allowing $T_{B(\infty)}$ to vary using the nonlinear least-squares procedure described above again resulted in similar values; $T_{B(\infty)} = 880$ and 950 K, respectively. The values are considered to be within experimental uncertainty of each other. These two values were averaged resulting in $T_{B(\infty)} = 915$ K and used to fit the boiling points of a few other homologous series for which only a few boiling points are available. The results are reported in Table 7. A similar limiting boiling temperature of 899 K for the *n*-perfluoroalkanes using a different empirical approach has been reported.¹⁴

The critical temperatures¹⁵ of perfluoropropane through to perfluorodecane were analyzed according to eq 7 by nonlinear least squares. Allowing $T_{C(\infty)}$ to vary resulted in a minimum when $T_{C(\infty)} = 920$ K, 5 K from the mean value of $T_{B(\infty)}$. For the perfluorinated alkanes, the critical and boiling temperatures of the perfluorinated series also converge in the limit. A value of $T_{C(\infty)} = 915$ K was used in all subsequent calculations requiring $T_{C(\infty)}$ and $T_{B(\infty)}$ for the perfluorinated series. The quality of the fit using this value is illustrated in Figure 5 by the solid squares that represent the experimental values and the dotted line (calculated). The two sets of values for a_C and b_C in eq 7 are reported in Table 8.

Critical pressures for the perfluorinated alkanes are available for C_3 to C_{10} . Application of eq 9 to model P_C using a value for $P_{C(\infty)} = 0.101$ MPa results in the fit reproduced as the solid diamonds in Figure 9. The adjustable parameters a_{PC} and b_{PC} derived from the nonlinear least-squares treatment are reported in Table 9 along with the standard deviation associated with the fit. As with series related to polyethylene, a limiting pressure of 0.1 MPa is certainly plausible for the perfluorinated hydrocarbons as well.

Far fewer vaporization enthalpies are available for the *n*-perfluoroalkanes. Only eight are reported in a recent compendium.¹⁶ These vaporization enthalpies, measured at different temperatures, were adjusted to their respective boiling points using eq 10¹⁷

$$\Delta_l^g H_m(T_B) = \Delta_l^g H_m(T_m) + [10.58 + 0.26C_{pl}][T_m - T_B] \quad (10)$$

The second term in eq 10 has usually been used to adjust vaporization enthalpies from the mean temperature of measurement, T_m , to $T = 298.15$ K and should be ap-

plicable in adjusting vaporization enthalpies to T_B provided the term $[T_m - T_B]$ is not large. The largest temperature correction was 78 K; most were considerably smaller. The C_{pl} term refers to the heat capacity of the liquid fluorocarbon, and this term was estimated using a group additivity approach.¹⁸

The behavior of $\Delta_l^g H_m(T_B)$ of the *n*-perfluoroalkanes according to the predictions of eq 8 is illustrated by the dashed lines in Figures 6 and 7; the triangles represent experimental data. According to Figure 6, eq 8 predicts that the maximum in $\Delta_l^g H_m(T_B)$ for the perfluorinated alkanes will be reached just slightly below 50 repeat units and will be lower than the maximum value for the *n*-alkanes. A maximum value of about 50 kJ·mol⁻¹ is predicted by eq 8. The *n*-perfluoroalkanes also behave differently in Figure 7. Unlike the corresponding hydrocarbons, $\Delta_l^g S_m(T_B)$ of the *n*-perfluoroalkanes decreases with increasing number of repeat units, N . It is not known whether similar behavior will be observed for other homologous series that converge to polytetrafluoroethylene).

Boiling Temperature, Critical Temperature, and Pressure Estimations of Homologous Series

There is considerably more boiling temperature data than critical data available in the literature. The empirical observation that the boiling temperature and critical temperature converge according to this model can be quite useful in estimating critical temperatures using eq 7. For the two series investigated, $T_{B(\infty)}$ and $T_{C(\infty)}$ have been evaluated; all that is needed are a few experimental boiling and/or critical temperatures to evaluate the a and b terms in eq 3 and 7. Values of T_B and T_C for the remaining members of any homologous series related to polyethylene and polytetrafluoroethylene can then be estimated. Estimations of critical pressures can also be achieved in a similar manner using eq 9 and $P_{C(\infty)} = 0.101$ MPa.

Figure 10 illustrates the correlation observed between calculated and experimental boiling temperatures using eq 3 and $T_{B(\infty)} = 1217$ K for hydrocarbons related to polyethylene (●) and $T_{B(\infty)} = 915$ K for the perfluorinated analogues (▲). The correlation obtained between calculated and experimental critical temperatures using eq 7 and $T_{C(\infty)} = 1217$ K for hydrocarbons related to polyethylene (●) and $T_{C(\infty)} = 915$ K for the perfluorinated analogues (▲) is reproduced in Figure 11. Similarly, Figure 12 illustrates the correlation between calculated and experimental critical pressures assuming a limiting critical pressure of 1 atm. The standard deviation between experimental and

367
368
369
370
371
372
373
374
375
376
377
378
379
380
381
382
383
384
385
386
387
388
389
390
391
392
393
394
395
396
397
398
399
400
401
402
403
404
405
406
407411
412
413
414
415
416
417
418
419
420
421
422
423
424
425
426
427
428
429
430
431
432
433
434
435
436
437
438
439
440
441
442
443
444
445
446
447
448
449
450
451
452
453
454
455
456
457

H Journal of Chemical and Engineering Data

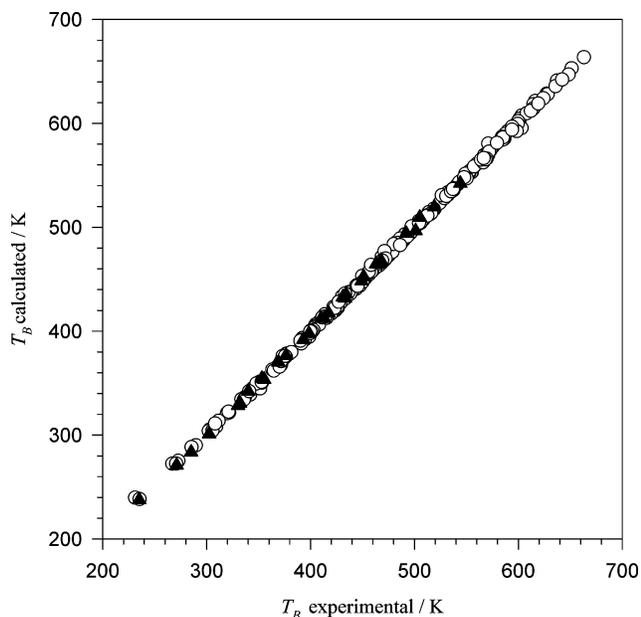


Figure 10. Calculated boiling temperatures, T_B , vs experimental values: \circ , series related to polyethylene using $T_B^{(\infty)} = 1217$ K; \blacktriangle , series related to polytetrafluoroethylene using $T_B^{(\infty)} = 915$ K. The equation of the line is given by: $T_{B(\text{calc})} = (1.000 \pm 0.001)T_{B(\text{expt})} + (0.117 \pm 2.23)$; correlation coefficient $r^2 = 0.9994$ for 262 observations.

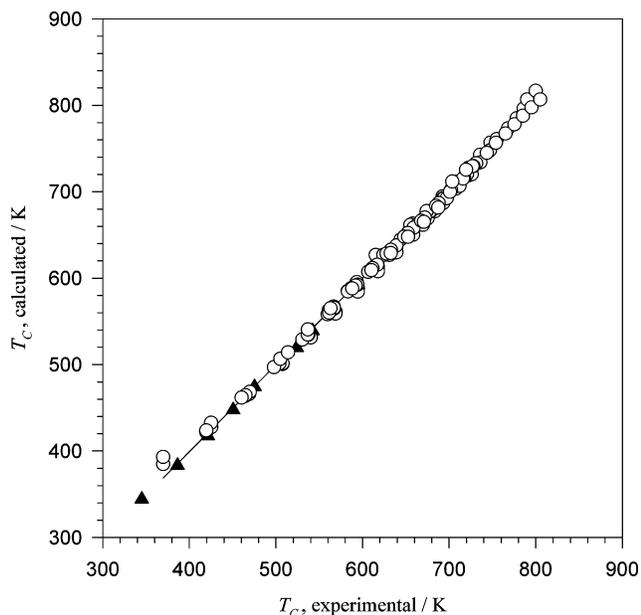


Figure 11. Calculated critical temperatures, T_C , vs experimental values: \circ , series related to polyethylene using $T_C^{(\infty)} = 1217$ K; \blacktriangle , series related to polytetrafluoroethylene using $T_C^{(\infty)} = 915$ K. The equation of the line is given by: $T_{C(\text{calc})} = (1.003 \pm 0.006)T_{C(\text{expt})} - (2.07 \pm 5.22)$; correlation coefficient $r^2 = 0.9968$ for 106 observations.

boiling temperatures calculated using $T_B^{(\infty)} = 1217$ for series related to polyethylene was ± 2.3 K (232 entries); for series related to polytetrafluoroethylene using $T_B^{(\infty)} = 915$ K, the uncertainty was ± 1.8 K (30 entries). Critical temperatures and pressures could be reproduced with a standard deviation of ± 5.2 K (106 entries) and ± 0.056 kPa (77 entries), respectively.

Boiling temperatures are relatively easy to measure; measurement of critical temperatures and pressures is more challenging. It appears that use of boiling tempera-

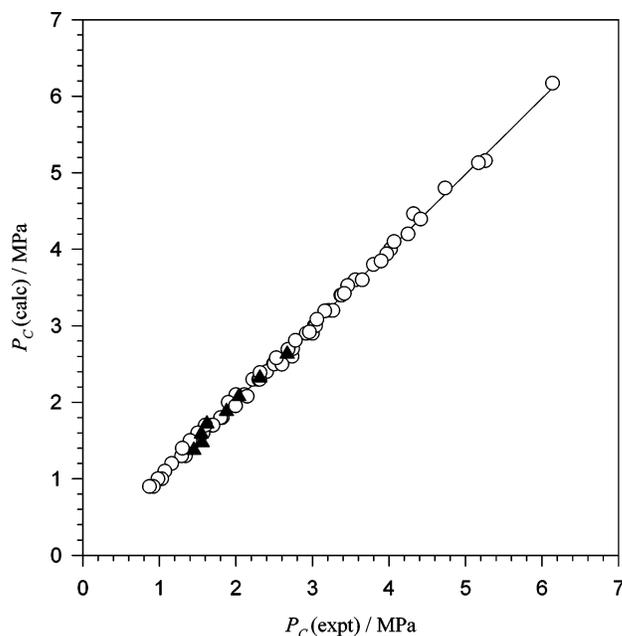


Figure 12. A comparison of calculated vs experimental critical pressures, P_C , using eq 9 and a value of $P_C^{(\infty)} = 0.101$ MPa: \circ , series related to polyethylene; \blacktriangle , series related to polytetrafluoroethylene. The equation of the line is given by: $P_{C(\text{calc})} = (0.9909 \pm 0.006)P_{C(\text{expt})} - (0.028 \pm 0.055)$; correlation coefficient $r^2 = 0.9975$ for 77 observations.

tures to evaluate $T_C^{(\infty)}$ and a few carefully spaced critical temperature and pressure measurements can result in reasonable estimates of a homologous series for intermediate and extrapolated values of N provided the extrapolation is kept reasonably close to the experimental values.

Discussion

The behavior predicted for T_B , T_C , and $\Delta_l^g H_m(T_B)$ of an increasing chain of repeat units, N , is not intuitively obvious. These properties are molecular properties whose physical meaning may change as the size of the molecule increases. Take $\Delta_l^g H_m(T_B)$ as an example. Vaporization enthalpy at the boiling temperature is a measure of the energy necessary to break attractive intermolecular forces at work. Consider an increasing chain of repeat units. Provided the chain is flexible, the chain will coil back on itself as it becomes larger.⁷ The proportion of intramolecular interactions will eventually increase at the expense of the intermolecular ones if the molecule gets large enough. Thus it does not seem unreasonable that $\Delta_l^g H_m(T_B)$ may begin to decrease as some point. On the molecular level, $\Delta_l^g H_m(T_B)$ focuses only on the interplay between inter- and intramolecular interactions, both of which are short range. Longer-range interactions are ignored, and in the limit, the concept of intermolecular interactions becomes moot when $N \rightarrow \infty$. Nevertheless, the model seems useful in mimicking the behavior of T_B , T_C , and P_C as a function of N at the level of interest to chemists and the conclusions reached by treatment of the experimental T_B , T_C , and P_C data appear to be internally self-consistent.

Summary

The behavior of T_B , T_C , and $\Delta_l^g H_m(T_B)$ observed in this study suggests that these properties can be successfully treated as asymptotically approaching finite limits. The results do suggest that the linear behavior first observed in plots of $\Delta_l^g H_m(T_B)$ vs $\Delta_l^g S_m(T_B)$ that suggested hyperbolic behavior of T_B as a function of N , however, must be

468
469
470
471
472
473
474
475
476
477
478
479
480
481
482
483
484
485
486
487
488
489
490
491
492
493
494
495
496
497
498
499
500
501
502
503

504 more complex. Hyperbolic eqs 3 and 7, prompted by the
 505 linearity observed between $\Delta_i^{\circ}H_m(T_B)$ and $\Delta_i^{\circ}S_m(T_B)$, suc-
 506 cessfully model T_B and T_C and appear useful in estimating
 507 them. A limiting critical pressure of 0.1 MPa is also
 508 plausible according to this analysis. The boiling tempera-
 509 tures of polyethylene and polytetrafluoroethylene have
 510 been evaluated as approximately 1200 and 900 K, in good
 511 agreement with earlier work.¹⁰ For homologous series that
 512 approach the structures of polyethylene and polytetrafluoro-
 513 ethylene in the limit, only a few experimental values are
 514 necessary to provide estimates for most of the series
 515 experimentally accessible. More useful perhaps is the use
 516 of boiling temperatures to obtain estimates of $T_B(\infty)$ of a
 517 series; used as a model for $T_C(\infty)$, this together with a few
 518 experimental critical temperatures and pressures can
 519 afford these critical properties for much of the series. In
 520 summary, the use of the hyperbolic functions described
 521 above to model T_B , T_C , and P_C provide some predictive
 522 advantages over the use of other polynomials that result
 523 in functions that initially approach each other but ulti-
 524 mately diverge as $N \rightarrow \infty$.

525 Acknowledgment

526 I would like to thank Professors Joel F. Liebman, Manuel
 527 J. Monte, and Harold H. Harris for some very useful
 528 comments and suggestions.

529 Supporting Information Available:

530 Tables including the experimental boiling temperatures,
 531 vaporization enthalpies, and references and boiling tempera-
 532 tures calculated using the protocols described in the text are
 533 available free of charge via the Internet at <http://pubs.acs.org>.

534 Literature Cited

- 535 (1) (a) Chickos, J.; Hesse, D.; Hosseini, S.; Nichols, G.; Webb, P.
 536 Sublimation Enthalpies at 298.15 K Using Correlation Gas
 537 Chromatography and Differential Scanning Calorimetry Mea-
 538 surements. *Thermochim. Acta* **1998**, *313*, 101–110. (b) Chickos,
 539 J. S.; Hillesheim, D. M.; Verevkin, S.; Roux, M. V.; Temprado,
 540 M.; Segura, M.; Notario, R. DeMasters, D. E.; Liebman, J. F. The
 541 Energetics of the Isomeric 1- and 2-Naphthoic Acids: Context,
 542 Quantum Chemical Calculations and Thermochemical Measure-
 543 ments. *Mol. Phys.* **2003**, *101*, 1311–1318.
 544 (2) Allen, J. O.; Sarofim, A. F.; Smith, K. A. Thermodynamic
 545 Properties of Polyaromatic Hydrocarbons in the Subcooled Liquid
 546 State. *Polycyclic Aromat. Compd.* **1999**, *13*, 261–283.
 547 (3) Chickos, J. S.; Nichols, G.; Ruelle, P. The Estimation of Melting
 548 Points and Enthalpies of Fusion Using Experimental Solubilities,
 549 Estimated Total Phase Change Entropies, and Mobile Order and
 550 Disorder Theory. *J. Chem. Inf. Comput. Sci.* **2001**, *42*, 368–374.

- (4) Chickos, J. S.; Nichols, G. Simple Relationships for the Estimation
 551 of Melting Temperatures of Homologous Series. *J. Chem. Eng.*
 552 *Data* **2002**, *46*, 562–573.
 553 (5) Somayajulu, G. R. The Melting Points of Ultralong Paraffins and
 554 Their Homologues. *Int. J. Thermophys.* **1990**, *11*, 555–572.
 555 (6) Woolf, A. A. Relations between the Boiling Points of Perfluoro-
 556 Ethers, Perfluoroalkanes and Normal Alkanes. *J. Fluorine Chem.*
 557 **1993**, *63*, 19–24.
 558 (7) Kreglewski, A.; Zwolinski, B. J. A New Relation for Physical
 559 Properties of *n*-Alkanes and *n*-Alkyl Compounds. *J. Phys. Chem.*
 560 **1961**, *65*, 1050–1052.
 561 (8) Kurata, M.; Ishida, S. Theory of Normal Paraffin Liquids. *J.*
 562 *Chem. Phys.* **1955**, *23*, 1126–1131.
 563 (9) Wilhoit, R. C.; Zwolinski, B. J. Handbook of Vapor Pressures and
 564 Heats of Vaporization of Hydrocarbons and Related Compounds.
 565 Publication 101, Thermodynamics Research Center, Texas A &
 566 M University, College Station, TX, 1971.
 567 (10) Somayajulu, G. R. The Critical Constants of Long Chain Normal
 568 Paraffins. *Int. J. Thermophys.* **1991**, *12*, 1039–1062.
 569 (11) (a) Ambrose, D.; Tsonopoulos, C. Vapor–Liquid Critical Properties
 570 of Elements and Compounds. 2. Normal Alkanes. *J. Chem. Eng.*
 571 *Data* **1995**, *40*, 531–546. (b) Gude, M.; Teja, A. S. Vapor–Liquid
 572 Critical Properties and Compounds. 4. Aliphatic Alkanols. *J.*
 573 *Chem. Eng. Data* **1995**, *40*, 1025–1036. Daubert, T. E. Vapor–
 574 Liquid Critical Properties of Elements and Compounds. 5.
 575 Branched Alkanes and Cycloalkanes. *J. Chem. Eng. Data* **1996**,
 576 *41*, 365–372. (c) Tsonopoulos, C.; Ambrose, D. Vapor–Liquid
 577 Critical Properties of Elements and Compounds. 6. Unsaturated
 578 aliphatic Hydrocarbons. *J. Chem. Eng. Data* **1996**, *41*, 645–656.
 579 (d) Kudchadker, A. P.; Ambrose, D.; Tsonopoulos, C. Vapor–
 580 Liquid Critical Properties of Elements and Compounds. 7. Organic
 581 Compounds Other Than Alkanols and Cycloalkanol. *J. Chem.*
 582 *Eng. Data* **2001**, *46*, 457–479.
 583 (12) Ambrose, D. NPL Report Chemistry 92, National Physical
 584 Laboratory, Teddington, Middlesex UK, 1978.
 585 (13) The use of a quintic equation in X gives an overall better fit;
 586 positions of the maximum in Figures 6 and 7 are not appreciably
 587 affected.
 588 (14) Woolf, A. A. Relationships between the Boiling Points of Perfluoro-
 589 Ethers, Perfluoroalkanes and Normal Alkanes. *J. Fluorine Chem.*
 590 **1993**, *63*, 19–25.
 591 (15) Vandana, V.; Rosenthal, D. J.; Teja, A. S. The Critical Properties
 592 of Perfluoro *n*-Alkanes. *Fluid Phase Equilib.* **1994**, *99*, 209–218.
 593 (16) Chickos, J. S.; Acree, W. E., Jr. Enthalpies of Vaporization of
 594 Organic and Organometallic Compounds, 1880–2002. *J. Phys.*
 595 *Chem. Ref. Data* **2003**, *32*, 515–878.
 596 (17) Chickos, J. S.; Hesse, D. G.; Liebman, J. F. A Group Additivity
 597 Approach for the Estimation of Heat Capacities of Organic Liquids
 598 and Solids at 298 K. *Struct. Chem.* **1993**, *4*, 261–269.
 599 (18) Each carbon was treated as a quaternary carbon; the following
 600 values were used: $C_Q = 14$; $F = 16.2 \text{ J mol}^{-1} \text{ K}^{-1}$. Chickos, J. S.;
 601 Hesse, D. G.; Liebman, J. F. Heat Capacity Corrections to a
 602 Standard State: A Comparison of New and Some Literature
 603 Methods for Organic Liquids and Solids. *Struct. Chem.* **1993**, *4*,
 604 271–278.
 605

Received for review August 11, 2003. Accepted February 12, 2004. I
 606 would like to thank the University of Missouri Research Board for
 607 partial support.
 608

JE030211U

609